

SikaRepair 222

Application Instructions



SikaRepair 222

- ▲ One-component
- ▲ Early strength gaining
- ▲ Cementitious
- ▲ Patching material for horizontal repair of concrete.



SikaRepair 222

▲ Where to use:

- On, above, and below grade on concrete and mortar.
- Repair material for spalled horizontal concrete surfaces, walkways, ramps, steps, etc.



SikaRepair 222

▲ Packaging:

- SikaRepair SHB - 50 lb. bag.
- SikaLatex R – 1 gal. plastic jug.

▲ Coverage:

- .42 cu. ft./bag
- 726 cu. inches./bag



Surface Preparation

- ▲ **Cementitious Substrates:**
 - Should be clean and sound.
 - Remove contaminants and bond inhibiting materials from repaired area.
 - Obtain exposed/fractured aggregate surface ~1/8 to 1/4 inch profile (ICRI CSP 6 & above).
 - Substrate must be saturated surface dry (SSD) with no standing water.



Surface Preparation


▲ Cementitious Substrates:

- Surface should be cleaned and roughened to create a profile.



Surface Preparation


- ▲ Saw cut around perimeter of repair area to achieve a minimum 3/8" shoulder.
- ▲ Eliminates feathered edges giving a clean repair transition

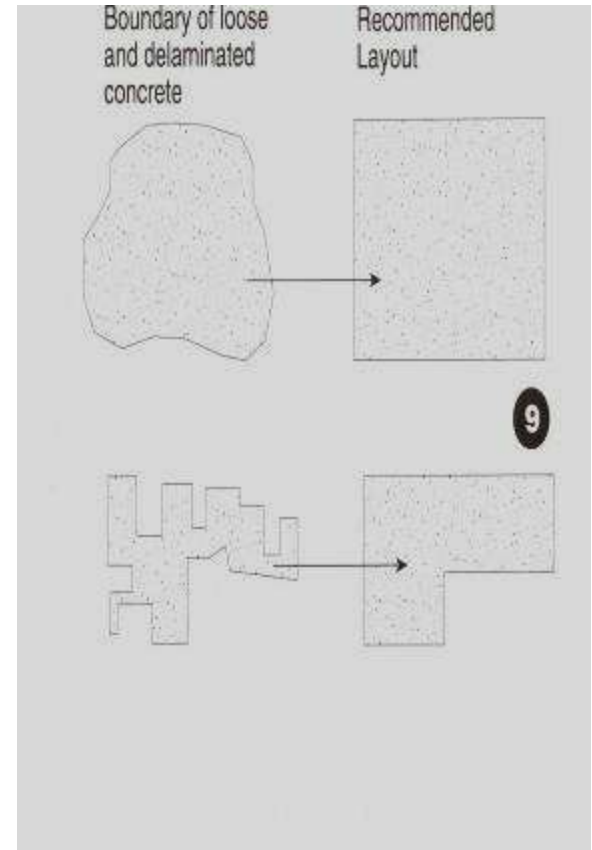

Surface Preparation

▲ Steel:

- Remove all corrosion and contaminants from exposed steel.
- Surface should be cleaned thoroughly by blast cleaning or mechanical means.
- Exposed steel should be cleaned to white steel.
- If half of the diameter is exposed, chip behind bar, 1/2" minimum for mortar only.

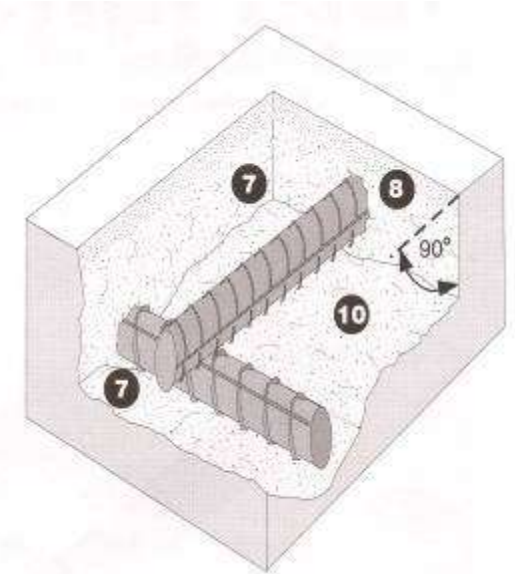

Steel Preparation

- ▲ Steel should be cleaned to a bright metal finish.



Tools Required

- ▲ 1/2" Drill Motor.
- ▲ Low speed drill 400-600 rpm.
- ▲ Large mixing paddle
- ▲ Margin trowel



Mixing

- ▲ Pour Water or Latex R into clean pail.
- ▲ Leave approximately 1" of Water or Latex R in jug.



Mixing

- ▲ Add SikaRepair 222 to pail with Water or Latex R already inside, while mixing continuously.



Mixing

1. Water or Latex R $\frac{3}{4}$ -1 gallon of liquid.
2. Start with adding liquid to the mixing container.
3. Slowly add powder.
4. Once all the powder is added mix for **3 minutes**.
5. Do not add any more than the recommended liquid.



Mixing

1. While mixing for 3 minutes stop to scrape after 1.5 minutes down the sides to insure all material is fully mixed.
2. Add additional Water or Latex R for desired consistency.
3. Most cases you will have liquid left.
4. Thorough mixing and proper proportioning is necessary.




SR 222 - Application

- ▲ Apply the mortar to the patch area while the Armatec 110 EpoCem is still wet.
- ▲ If Armatec is not used as a bonding agent, SSD the surface and scrub coat the repair mortar into the substrate filling all pores and voids.



SR 222 - Application

- ▲ Apply scrub coat to substrate, filling all pores and voids
- ▲ While scrub coat is wet, apply SikaRepair 222
- ▲ Press mortar behind rebar and make sure the material is consolidated and compacted fully.

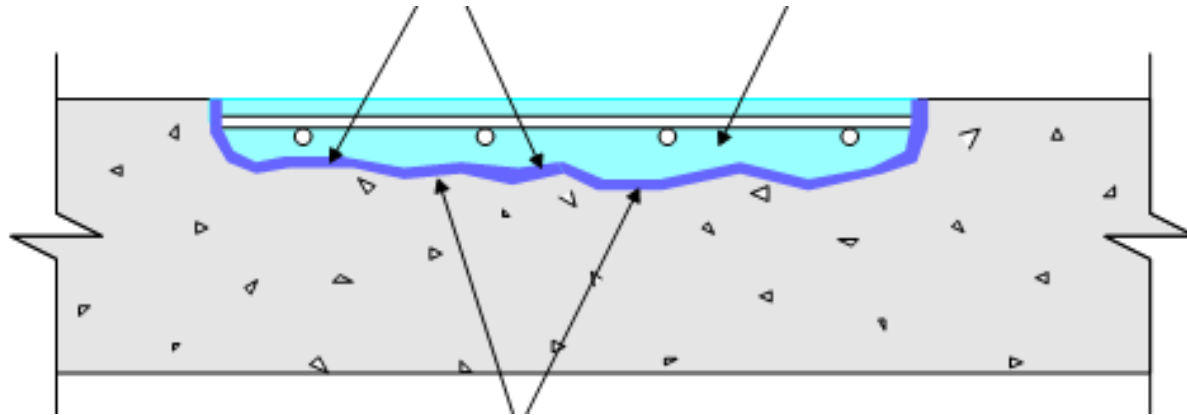

SR 222 - Application

- ▲ Complete filling patch area.
- ▲ Work mortar from the center of the patch to the outside.



Min / Max application thickness

- ▲ Water and diluted Latex R
 - Neat *Min* (1/4 inch) *Max*(1.0 inch)
 - Extended *Min* (1.0 inch) *Max* (4.0 inch)
- ▲ Undiluted Latex R
 - Neat *Min* (1/8 inch) *Max*(1.0 inch)
 - Extended *Min* (1.0 inch) *Max* (4.0 inch)
- ▲ SikaRepair 222 can be extended with aggregate.



SikaRepair 222 - Finish

- ▲ After filling patch section, allow mortar to set to desired stiffness.
- ▲ Then finish with steel, wood, plastic floats, or damp sponge float to attain look required.



SikaRepair 222 - Finish

- ▲ To assist in the finishing of the SikaRepair use SikaFilm.
 - SikaFilm is a finishing aid that also retards moisture evaporation.



SikaRepair 222 - Finish

- ▲ You can use a steel trowel to attain a smooth surface.



Sponge Float Finish

- ▲ You can use Sponge float to attain a textured surface.



SikaRepair Curing

- ▲ Cure as per ACI recommendations. Curing is required.
- ▲ Moist cure with wet burlap and polyethylene, a fine mist of water or water-based curing compound.
- ▲ Moist curing should commence immediately after finishing.
- ▲ Protect newly applied material from direct sun light, wind, rain and frost.



SikaRepair 222

Sika Product Data Sheets can be obtained via:

www.sikaconstruction.com

Refer to data sheets for specific information on each Sika product.

